

2015-10-15

Characterisation, Quantity and Sorptive Properties of Microplastics Extracted From Cosmetics

Napper, IE

<http://hdl.handle.net/10026.1/3502>

10.1016/j.marpolbul.2015.07.029

Marine Pollution Bulletin

Elsevier

All content in PEARL is protected by copyright law. Author manuscripts are made available in accordance with publisher policies. Please cite only the published version using the details provided on the item record or document. In the absence of an open licence (e.g. Creative Commons), permissions for further reuse of content should be sought from the publisher or author.

**Characterisation, Quantity and Sorptive Properties of Microplastics Extracted
From Cosmetics**

Imogen E. Napper^a, Adil Bakir^{ab}, Steven J. Rowland^b, Richard C. Thompson^a

*^a Marine Biology and Ecology Research Centre (MBERC) School of Marine Science and Engineering,
Plymouth University, Drake Circus, Plymouth, Devon, PL4 8AA*

*^b Petroleum and Environmental Geochemistry Group (PEGG) School of Geography, Earth and
Environmental Sciences, Plymouth University, Drake Circus, Plymouth, Devon, PL4 8AA*

Corresponding author: Imogen.Napper@Plymouth.ac.uk

**This is the Authors pre-print version of the unpublished manuscript.
As such it is not the final version. Please refer to Marine Pollution
Bulletin to read the final article.**

21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43

Abstract

Cosmetic products, such as facial scrubs, have been identified as potentially important primary sources of microplastics to the marine environment. This study characterises, quantifies and then investigates the sorptive properties of plastic microbeads that are used as exfoliants in cosmetics. Polyethylene microbeads were extracted from several products, and shown to have a wide size range (mean diameters between 164 to 327 μm). We estimated that between 4594 – 94500 microbeads could be released in a single use. To examine the potential for microbeads to accumulate and transport chemicals they were exposed to a binary mixture of ^3H -phenanthrene and ^{14}C -DDT in seawater. The potential for transport of sorbed chemicals by microbeads was broadly similar to that of polythene (PE) particles used in previous sorption studies. In conclusion, cosmetic exfoliants are a potentially important, yet preventable source of microplastic contamination in the marine environment.

Keywords:

- Microplastic; Exfoliating Microbeads; Polyethylene; Ocean pollution; Contaminant

44

45

46

47 **1. Introduction**

48

49 Plastics provide a diverse range of inexpensive, lightweight, strong, durable and
50 corrosion-resistant products (Thompson *et al.*, 2009b). The success of plastics as
51 materials has been substantial and they are used in a wide range of applications.
52 This versatility, together with their low cost, has resulted in the annual worldwide
53 production of around 300 million tonnes (Plastics Europe. 2014). Approximately 50%
54 of production is used to make packaging, much of which is used in disposable
55 applications. This creates a major waste management problem, with plastics
56 accounting for approximately 8-10% of all the waste generated in the UK (Barnes *et*
57 *al.*, 2009; Hopewell *et al.*, 2009).

58

59 Around 700 species of marine organism have been reported to encounter marine
60 debris in the natural environment, with plastic debris accounting for over 90% of
61 these encounters (Gall and Thompson, 2015). Large plastic items, such as
62 discarded fishing rope and nets, can cause entanglement of invertebrates, birds,
63 mammals, and turtles (Carr, 1987; Eerkes-Medrano *et al.*, 2015; Fowler, 1987; Laist,
64 1997) but the marine environment is also contaminated with much smaller
65 microplastics particles (defined by NOAA as <5mm). These have been reported at
66 the sea surface (Law and Thompson 2014), on shorelines (Claessens *et al.*, 2011),

and on the sea bed (Van Cauwenberghe et al., 2013). The sources of microplastics include fragmentation of larger items (secondary sources), and direct inputs of microplastic sized particles, such as microbeads used in cosmetics and pre-production pellets (primary sources). It is important to understand the relative importance of these sources as well as the size and abundance of microplastic particles released, since this will influence encounter rate and availability to biota (Cole et al 2011; Teuten et al., 2007; Thompson et al., 2009a).

There is growing evidence that the amount of microplastics in marine waters is increasing, with unknown ecotoxicological consequences (Goldstein et al., 2012). Fendall and Sewell (2009) reported on microbeads used as “scrubbers” in cosmetics products, which they described as being up to 500 μm in diameter, being released into the natural environment and potentially available to organisms. Ingestion of microplastics, has been reported for a wide range of marine organisms including deposit and suspension feeders (Browne et al., 2008; Graham and Thompson, 2009), crustaceans (Murray and Cowie, 2011), fish (Boerger et al., 2010), marine mammals (Denuncio et al., 2011), and seabirds (Avery-Gomm et al., 2012; Van Franeker et al., 2011). However, the extent, if any, to which chemicals sorbed onto, or incorporated into plastics can desorb from plastic particles, and transfer to the tissues of marine organisms is less clear. Recent experimental trials provide evidence for the role of plastics in the transfer of chemicals with subsequent adverse physiological effects (Besseling et al., 2013; Rochman et al., 2013), but studies based on bioaccumulation models concluded that the transfer of contaminants from plastics to marine

organisms upon ingestion is of limited importance compared to other pathways (Gouin et al., 2011; Koelmans et al., 2013).

Microplastics have been used to replace natural exfoliating materials (for example, pumice, oatmeal, apricot or walnut husks) in cosmetics and have been reported in a variety of products such as hand-cleansers, soaps, toothpaste, shaving foam, bubble bath, sunscreen, shampoo and facial scrubs (Fendall and Sewell, 2009; Gregory, 1996; Zitko and Hanlon, 1991; UNEP, 2015).

Industry uses the terms ‘microbeads’ to describe microplastic particles present as ingredients in personal care and cosmetic products; they may also be called microspheres, nanospheres, plastic particulates (UNEP, 2015). Around 93% of the ‘microbeads’ used in cosmetics are polyethylene (PE), but they can also be made of polypropylene (PP), PE terephthalate (PET), polymethyl methacrylate (PMMA) and nylon (Gouin et al., 2015; Eriksen et al., 2013; UNEP, 2015). Microbeads are likely to be transported to wastewater treatment plants, where some will be captured in oxidation ponds or sewage sludge. However, due to their small size, it is anticipated that a substantial proportion will pass through filtration systems and enter aquatic environments (Fendall and Sewell, 2009).

Leslie et al. (2013), examined wastewater treatment plants that discharge into the North Sea, the Oude Maas River or the North Sea Canal and reported that the treated effluent contained on average 52 pieces of microplastics/L. Eriksen et al. (2013) also reported substantial amounts of multi-coloured microplastic spheres in surface waters of the Laurentian Great Lakes of the United States which were suspected to originate from consumer products. This provides evidence that microplastics are not all captured in sewage sludge of wastewater treatment plants and is of broad concern, since treated effluent from sewage disposal sites is discharged into a range of water bodies, including into inland waters, estuaries and the sea (DEFRA, 2002).

Gouin et al. (2011) estimated that the per capita consumption of microplastic used in personal care products for the U.S. population, based on the usage of PE microplastic beads used in personal care products, was approximately 2.4 mg per person⁻¹ per d⁻¹, indicating that the U.S. population may be emitting an estimated 263 tonnes per yr⁻¹ of PE microplastic (Gouin et al., 2011). To set this into perspective, in terms of its contribution to marine litter, this annual quantity is approximately equivalent to 25% of the total mass of plastic that is estimated to have accumulated in the North Atlantic Subtropical Gyre (Law et al., 2010; Gouin et al., 2011).

Facial scrubs are one type of cosmetic which contains microplastics as exfoliating agents. Due to this, such products could contribute microplastics contamination to the marine environment. Despite concerns about the potential for products containing microbeads to represent a major source of microplastics to the

environment, only one study has measured microplastics in facial scrubs (Fendall and Sewell, 2009), and there are no peer reviewed publications confirming the type or quantity of microplastic polymers used in facial scrubs. Here we examined six brands of facial scrubs manufactured by three companies and describe the microplastics (plastic microbeads) present, in terms of polymer type, colour, size, weight and abundance. We also investigated the sorptive properties of the microplastics in relation to the potential for transport of the POPs phenanthrene (Phe) and dichlorodiphenyltrichloroethane (DDT) and compared them with commercially available PE particles previously used in adsorption/desorption studies of persistent organic pollutants (POPs) (Bakir et al., 2012, 2014a, b; Teuten et al., 2007).

2. Methods

2.1 Sample preparation

Six major brands of facial scrubs were chosen, based on their prevalence in major supermarkets close to Plymouth UK. All of the products listed in their ingredients that they contained PE. Four replicates of each product were purchased, with each replicate sourced from a different supermarket to provide a representative sample.

Since the specific brand names of the products are not of particular relevance, they were labelled A-F.

Each facial scrub was a viscous liquid (A to D contained 150mL of product, E contained 125mL). The contents were subjected to vacuum filtration to obtain the

plastic particles. The procedure required mixing each product in approximately 1L of boiling water, followed by vacuum filtration over Whatman N°4 filter paper, then drying at 30°C to constant weight. Once dry, the particles were weighed by Precisa 2200C weighing scales and the residues were transferred into separate glass vials. A Kruskal-Wallis test was performed on the data, using R studio, to test whether the amount of microplastics per unit volume extracted differed between products ($p < 0.05$). This was followed by a *post-hoc* Nemenyi-Test to find which specific products significantly differed.

2.2 Visualisation and identification

Microplastics from each product were identified using Fourier transform infra-red spectroscopy (FTIR), using a Hyperion 1000 microscope (Bruker) coupled to an IFS 66 spectrometer (Bruker). The spectra obtained were compared to a spectral database of synthetic polymers (Bruker I26933 Synthetic fibres ATRlibrary).

Some non-plastic residues were extracted and separated from the plastic particles using Endecotts woven wire sieves of varying mesh size. The mass of plastic particles was recorded.

A Malvern Mastersizer 2000 laser particle sizer (MM2) was used to measure the size-frequency distributions (SFDs) of the extracted plastic into sixty-eight different

sized bands with logarithmic spacing (range 0.015 µm, to 2000 µm; Woolfe and Michibayashi, 1995). The resultant particle size distributions were expressed as a volume weighted mean from an average of twenty five measurements per product. The mean for each product was then calculated.

The number of plastic particles in each product, N , was estimated, assuming the particles were of spherical shape, using the following equations:

$$\text{i) } V_t = \frac{M_t}{D} \quad \text{ii) } V(\text{avg particle}) = \frac{4}{3}\pi r^3 \quad \text{iii) } N = \frac{V_t}{V(\text{avg particle})}$$

where V_t is the total volume of plastic extracted, M_t is the total mass of plastic extracted, D is the density, $V(\text{avg.p})$ is the mean volume of one particle, N is number of particles, and r is the radius.

For each product: equation i) allowed calculation of the total volume of microplastic extracted; equation ii) allowed calculation of the average volume of a microplastic particle from each product; by dividing the total volume of microplastic by the average volume of a microplastic particle, equation iii) allowed calculation of the approximate number of particles in each product. Particles were then visualised by scanning electron microscopy (JEOL, 7001F), imaging to describe both whole particles and their topography.

203

204

205

206

207 2.3 Sorption of pollutants to plastics

208

209 As part of a separate, but related study, microbead exfoliants were extracted from
210 shower gel and used to examine the adsorption of POPs by microbeads. The
211 microbeads from the shower gel products were extracted and identified by FTIR
212 following the same methods in sections 2.1 and 2.2. As these microbeads were
213 extracted from different brands of exfoliant products, they are labelled X, Y & Z.
214 These microbeads were exposed to Phe and DDT; the results were then compared
215 with sorption to ultra-high-molecular-weight (UHMW) PE particles used in a previous
216 sorption study (Bakir et al., 2014a, 2014b, 2012).

217

218 Adsorption experiments were conducted in an ISO9001 accredited radioisotope
219 facility at the Plymouth University. ^3H -Phe and ^{14}C -DDT were selected as
220 contaminants in this study to allow simultaneous quantification and to compare with
221 past studies (Bakir et al., 2012). 10 mg of either UHMW PE or the extracted
222 microbeads were placed into three glass centrifuge tubes (50 mL) and 5 μL of ^{14}C -
223 DDT and 16 μL of ^3H -Phe were added to the walls of the tubes. The solvent was
224 allowed to evaporate and 25 mL of seawater (35 psu, 59.3 ± 0.26 mS) was added
225 and the tubes were equilibrated for 48 hours (Bakir et al., 2014a) in the dark at 18 °C

under continuous horizontal, rotary agitation at 220 rpm. All experiments were carried out in triplicate. The concentration of contaminant was determined in the aqueous and solid phase by counting the β decay from the ^{14}C -contaminant by liquid scintillation counting (LSC) as outlined in Bakir et al. (2012). The amount of contaminant in each phase was quantified using a calibration curve prepared by counting known amounts of the contaminant.

The single point distribution coefficient, single point K_d , was calculated using the equation:

$$(iv) K_d = [q_e]_{solid} / [C_e]_{aq.}$$

where q_e is the amount of contaminant adsorbed onto plastic ($\mu\text{g kg}^{-1}$) at equilibrium and C_e is the contaminant concentration in the aqueous phase at equilibrium ($\mu\text{g L}^{-1}$).

2.4 Statistical analysis

A two-factor ANOVA, with contaminants and the microbead type considered as fixed factors, was used to characterise any significant differences ($p < 0.05$) between the distribution coefficients calculated from the sorption of Phe and DDT onto microbeads. Cochran's test was used to ensure that the data fulfilled the pre-requisites for parametric analysis and the appropriate data were $\ln(x+1)$ transformed. Student-Newman-Keuls (SNK) tests were then used to identify any significant terms. The tests were carried out using GMAV5 software (Underwood et al., 2002) and are presented in the supplementary information.

248

249

250

251

252

253 **3.0 Results**

254 **3.1 Extraction and Identification**

255

256 All of the products contained microplastic particles of PE, which was in agreement
257 with their stated ingredients. Product C also contained green and yellow particles
258 that were slightly larger than the PE microbeads. These could not be identified by
259 FTIR using the Bruker spectral database and were removed from the samples via
260 sieving and are not included in any of the calculations. The collected solids from
261 product C also contained micro-‘glitter’. These ‘glitter’ particles were small and could
262 not be removed from the filter paper for further analysis. However, ‘glitter’ is
263 commonly manufactured from plastic, such as PE.

264

265 The weight of microplastic extracted varied significantly between products (Kruskal-
266 Wallis test, $p = 0.0012$, Fig 1); the products which were significantly different from
267 each other were C and E ($p = 0.0009$); D and E ($p = 0.0463$) (*post hoc* Nemenyi-
268 Test).

269

270

271

272

273

274 3.2 Size-Frequency Distributions

275

276 Microplastics from the facial scrubs showed polydispersed size ranges, each with
277 logarithmic bimodal distributions (Fig 2). Product B had the largest size range (10µm
278 to >2000 µm), whereas product A was the most homogenous, ranging from 8µm to
279 56µm, with the largest proportion of smaller particles. Size frequency by volume
280 distributions were used to calculate the mean diameters for each product. Products
281 D-F had similar volume-weighted mean diameters, which were 288.80 µm, 289.63
282 µm and 293.48 µm respectively. The particles in product B and C were larger, with
283 mean diameters of 326.83 µm and 317.91 µm, while product A was much smaller
284 with a mean diameter of 163.82 µm. The volume-weighted mean diameters were
285 used to estimate the number of particles in each product. Since the absolute density
286 of the extracted plastics was not known, we calculated estimates using a range of
287 standard densities. For PE these were, high (0.959 g/cm³), medium (0.940 g/cm³)
288 and low density (0.910 g/cm³).

289

Particle diameter, rather than the average weight in each product, was found to have the greatest effect on abundance estimates. Product E had on average 11.47 g of PE in each bottle, with a mean particle size of 289.63 μm , resulting in an estimated 6423 particles per mL. Whereas product A had less PE by weight with, on average, 6.11g in each bottle, but resulted in an estimate of 18906 particles per mL because the mean size was smaller (163.82 μm); being the highest quantity in any of the products. Product C had the second largest PE particles (317.91 μm), but the lowest particle abundance, with only 919 particles per mL. This data implies that the products tested could each contain between 137,000 and 2,800,000 microparticles (Figure 3). The quantity of particles was calculated using data for the volume mean diameter, however the size particle distribution had a tail of smaller particles, hence the particle abundances calculated are likely to be underestimates.

The shape and surface topography of the extracted microplastic particles was visualised by scanning electron microscopy. For all the brands, the extracted microplastics had a variety of shapes, including ellipses, ribbons, and threads, as well as irregular fragments (Fig 4). An exception was product F, which in addition to irregular shaped pieces, also contained smooth, blue, PE spheres that were substantially larger than the rest of the particles, but represented a small proportion of the total amount of plastics present. Some of these spheres were fragmenting (Fig 4).

The colour of microplastics used in the different products also varied (Table 1). All products contained white microplastics, but products A, D, E and F also contained coloured particles. The coloured microplastics in products D-F were larger than the

314 white plastics, but were less abundant. The white and pink microplastics in product A
315 were of similar size to each other.

316

3.3 Sorption of persistent organic pollutants

Visualisation of microbeads extracted from products X, Y, and Z showed they could be differentiated between “smooth” and “rough” forms. This particle shape differentiation was also observed in products A-F, where A-E contained "smooth" particles and product F contained both "smooth" and "rough" forms (Fig 4). Therefore, we considered sorption onto both morphologies. Results showed that microbeads extracted from the cosmetic products were able to sorb Phe and DDT from seawater (Fig 5). Sorption capacity for all plastics was significantly higher for DDT compared to Phe ($p < 0.05$, Table 2). The “rough” microbeads were more efficient at adsorbing POPs from seawater than “smooth” ones, probably due to increased surface area. The “rough” microbeads were also more similar in shape, surface texture and sorptive property for POPs to PE particles used in previous experiments (e.g. Bakir et al., 2012, 2014a, b; Teuten et al., 2007). There were some significant differences between adsorption by microbeads and adsorption by PE particles and the direction of these effects was that microbeads from cosmetics tended to adsorb lower concentrations of POPs than PE particles. However, broadly speaking, it would appear that results from previous studies on transport of chemicals by sorption on to plastic are comparable with the transport potential on microbeads.

4.0 Discussion

Microplastics found within cosmetics such as facial scrubs, will routinely be washed into sewers as a direct consequence of consumer use. Due to their size, a considerable proportion is likely to pass through preliminary sewage treatment screens (typically coarse, >6 mm, and fine screens, 1.5–6 mm) (Water Environment Federation, 2003). Effluent containing the microplastics would then be discharged into inland waters, estuaries and the oceans. A recent study reported that treated effluent from three sample sites in the Netherlands contained on average 52 microplastic particles/L (Leslie et al., 2013). Microbeads used as exfoliants in facial scrubs are likely to be an important primary source of microplastics contamination, due to the quantity of plastic used in each product.

When considering the potential consequences of the release of microbeads to the environment, if any, it is important to consider both the mass of plastic, and the number and size of the particles; the latter will have direct influence on the probability of encounters with wildlife.

The common application of facial scrub exfoliants is once per day, and it has been estimated that they are used by around 1.1 million women in the UK (Statista, 2013). Focussing on the products used in this study (A-F), and assuming that the typical daily amount used is 5mL, between 4594 – 94500 microplastic particles would have the potential to pass into the sewage system per use.

362 In terms of the mass of plastic entering the marine environment, previous work by
363 Gouin et al (2011) estimated that users in the U.S emit 2.4 mg of PE person⁻¹.d⁻¹,
364 amounting to an emission of 263 tonnes yr⁻¹. This estimate is calculated from data
365 on liquid soap consumption, and assumes that only 15% of the market is shared by
366 companies that use microplastic beads in their liquid soaps. However, many brands
367 do use exfoliating microbeads. Assuming that three out of four body exfoliants
368 contain microplastics (Marine Conservation Society, 2012), and that an estimate that
369 25% of the microplastic is caught by the sewage system, the UK population could
370 emit to the natural environment 40.5 – 215 mg of PE person⁻¹.d⁻¹, or between 16
371 and 86 tonnes yr⁻¹ (population of the UK in 2013: 64.1 million, (The World Bank,
372 2013) just from facial exfoliants. In order to set these quantities into context, by way
373 of comparison, between 2009 and 2014 inclusive, in its annual weekend beach clean,
374 MCS typically collect around 9 tonnes of litter per year (over an average length of
375 115km of UK shoreline).

376 The presence of microplastics in sewage sludge has been reported previously by
377 Browne et al. (2011), who found that former sewage disposal-sites on the seabed in
378 UK waters contained more microplastics than non-disposal reference sites,
379 highlighting the potential for microplastics to accumulate in aquatic habitats. The
380 occurrence of microplastics within the marine environment is now well documented
381 in the water column, at the sea surface and sediments (Law and Thompson 2014).
382 Microplastics also account for around 10% of all reports of ingestion of marine
383 debris, highlighting their importance as a component of marine debris (Gall and
384 Thompson, 2015). Their size makes them accessible to organisms with a range of
385 feeding methods, including: filter feeders (mussels, barnacles), deposit feeders
386 (lugworms) and detritivores (amphipods, sea cucumbers) and zooplankton (Wright et

al., 2013a; Graham and Thompson, 2009; Thompson et al., 2009; Browne et al., 2008). However, studies that quantify the abundance of microplastic predominately report elongated fibres. This may in part be due to the relative ease of detection of pieces with these shapes, since they differ from many natural particles found in sediments. Hence, the prevalence of microplastics with non-fibrous shapes (Fig 4), for example microbeads from facial scrubs, may be under-reported in environmental sampling (Desforges et al., 2014; Lusher et al., 2014; Gallagher et al., 2015).

There is no way of effectively removing microplastic contamination once it is in the environment. The materials are too dispersed, the scale is too vast, ecological damage would be caused by any remediation (tiny organisms would likely be removed along with the microplastics), and the costs would be extremely high (UNEP, 2015). Since plastic is highly resistant to degradation, the abundance of microplastics in the ocean is assumed to be increasing, thus increasing the probability of ingestion by biota (Law and Thompson, 2014). The majority of microplastics extracted from the facial products herein were white or blue. It has been suggested by Wright, et al. (2013b) that these colours are similar to various types of plankton, a primary food source for surface feeding fish, which are visual predators.

A further potential problem associated with microplastics contamination is the possibility of transport of hydrophobic contaminants by microplastics: such contaminants have been found to sorb onto their surface of plastics and may transfer to biota upon ingestion (Avio et al., 2015; Bakir et al., 2014b; Teuten et al., 2007).

Previous studies have shown that PE particles have the potential to sorb and concentrate a range of hydrophobic contaminants. This is of interest because these contaminants can be released in conditions resembling those in the gut of an organism (Bakir et al., 2014b) . However, at present, the environmental importance of plastics as a vector in the transport of contaminants is not known. Here we show that microbeads were able to adsorb greater amounts of DDT than Phe when both chemicals were present in a mixture. This was in agreement with previous work indicating that plastic showed a preferential affinity for DDT when present with Phe in a binary mixture (Bakir et al., 2012). The size and shape of microbeads was also found to be an important factor in their sorptive property for POPs and smooth microbeads were found to adsorb lower concentrations of POPs than rough ones. Rough microbeads were found to be most similar in their sorptive properties for POPs to commercially available PE used in chemical transport studies (e.g. Bakir, et al., 2012, 2014b; a; Teuten, et al., 2007). However, both types of microbeads were broadly similar in their sportive properties to the microplastics used in previous studies. Hence, on the basis of the experimental work here, it seems likely that conclusions regarding the potential role of microplastics as possible vectors in the transport of POPs in the environment could also be applied to transport by microbeads from cosmetics.

Rochman et al. (2013) investigated the transfer of hydrophobic organic compounds (PAHs, PCBs and PBDEs) from PE to the fish, Japanese medaka (*Oryzias latipes*) and the subsequent health effects. Plastic particles were exposed to natural marine

conditions, as opposed to laboratory exposures used in most previous studies. Environmental exposure will be highly dependent on the sites selected, which can be prone to variation. Results suggested the ingestion of virgin PE particles caused physiological stresses. However, the ingestion of contaminated PE particles led to the transfer of adsorbed contaminants, causing liver toxicity and pathology (Rochman et al., 2013). Laboratory studies using microplastic particles of polystyrene (Besseling et al., 2013) and PVC (Browne et al., 2013) have also indicated the potential for transfer of harmful chemicals with subsequent effects on biota. The present study showed that plastic particles present in cosmetics can be of varying size and shape and have differential affinities for sorption of POPs. Further work would be needed investigate the presence of chemicals such as pigments and dyes in microbeads, and their potential, if any, for migration from the polymer in either water or gut conditions.

The uneven topography of microplastics used in cosmetics could also provide habitats for diverse communities of microorganisms. A study by Zettler et al. (2013) described the presence of a rich eukaryotic and bacterial microbiota living on PE microplastic samples collected from the North Atlantic subtropical Gyre. Scanning electron microscope (SEM) images showed microbial cells embedded in pits on the plastic surface, and suggested that some members of this community could be accelerating the physical degradation of plastic; however this remains to be confirmed. The communities found on the plastic particles were distinct from surrounding surface water, indicating that plastic provides a novel habitat. Other studies have highlighted the potential for microplastic to act as vectors for microbial pathogens (Harrison et al., 2014).

Currently, there are reported to be eighty facial scrubs in the UK market, which according to their product labelling, contain plastic material amongst their ingredients (Beat the Microbead, 2015). However, some companies have indicated that they will voluntarily phase out microplastics from their products. This could possibly be due to research indicating the negative consequences of microplastics within the environment; Fendall and Sewell (2009) stated that the presence of microplastics in facial cleansers, and their potential use by millions of consumers world-wide, should be of increasing concern, whilst Andrady (2011) also reported that there is an urgent need to assess the future impact of increasing microplastics levels on the world's oceans. There have also been associated public awareness campaigns (eg. Beat the Microbead and Scrub it Out), urging consumers to boycott such products.

However, for the global market, usage statements vary within and between companies, with some stating they will remove all microplastics from all their products, while others say only PE will be removed. In some regions, legislation has been introduced; for example, Illinois and California (U.S.A) have banned the manufacture and sale of cosmetics that contain plastic microbeads, with similar legislation being proposed for New York, Michigan, and Ohio (but not yet adopted) (Driedger et al., 2015).

In conclusion, the present work characterised the microplastics in facial scrubs by describing the polymer type, colour, size, weight and abundance. This allowed for estimation that between 4594 and 94500 particles could be released into the environment per use. We also estimate that the UK population is emitting 40.5 – 215 mg of PE person⁻¹.d⁻¹, resulting in a total of 16-86 tonnes yr⁻¹. Particle size, rather

than the average weight in each product, was found to be important as it had the greatest effect on abundance estimates. Their small size also renders microbeads accessible to a wide range of organisms, and may facilitate the transfer of waterborne contaminants or pathogens. There are alternatives to the use of plastics as exfoliating particles (UNEP 2015); hence these emissions of microplastic are avoidable. Given the quantities of plastic particles reported here, and current concerns about the accumulation of microplastics in the ocean, it is important to monitor the extent to which manufacturers do voluntarily opt to remove microplastics from their products. Such monitoring will help to establish whether there is a need for further legislation.

Tables

Product	Colour of Microplastic Present
A	White and Pink
B	White
C	White
D	White and Light Blue
E	White and Dark Blue
F	White and Dark Blue

Table 1. *Colour of microplastics found within six facial scrub products.*

Particle type	POP	Aqueous phase	Glass wall	Solid phase	Total recovery
Product X beads	DDT	12	8	59	78
	Phe	43	1	24	68
Product Y particles	DDT	7	8	91	106
	Phe	13	3	65	81
Product Z beads	DDT	20	26	33	79
	Phe	64	2	6	73
Product Z particles	DDT	3	8	90	101
	Phe	11	5	60	75
UHMW PE	DDT	2	6	87	94
	Phe	7	2	80	89

530

531 **Table 2.** *Recovery (%) of phenanthrene (Phe) and DDT following sorption*
532 *experiments onto PVC and PE (average values displayed, n = 3).*

533

534

535

536

537

538

539

540

541


542

543

544

545

Figures

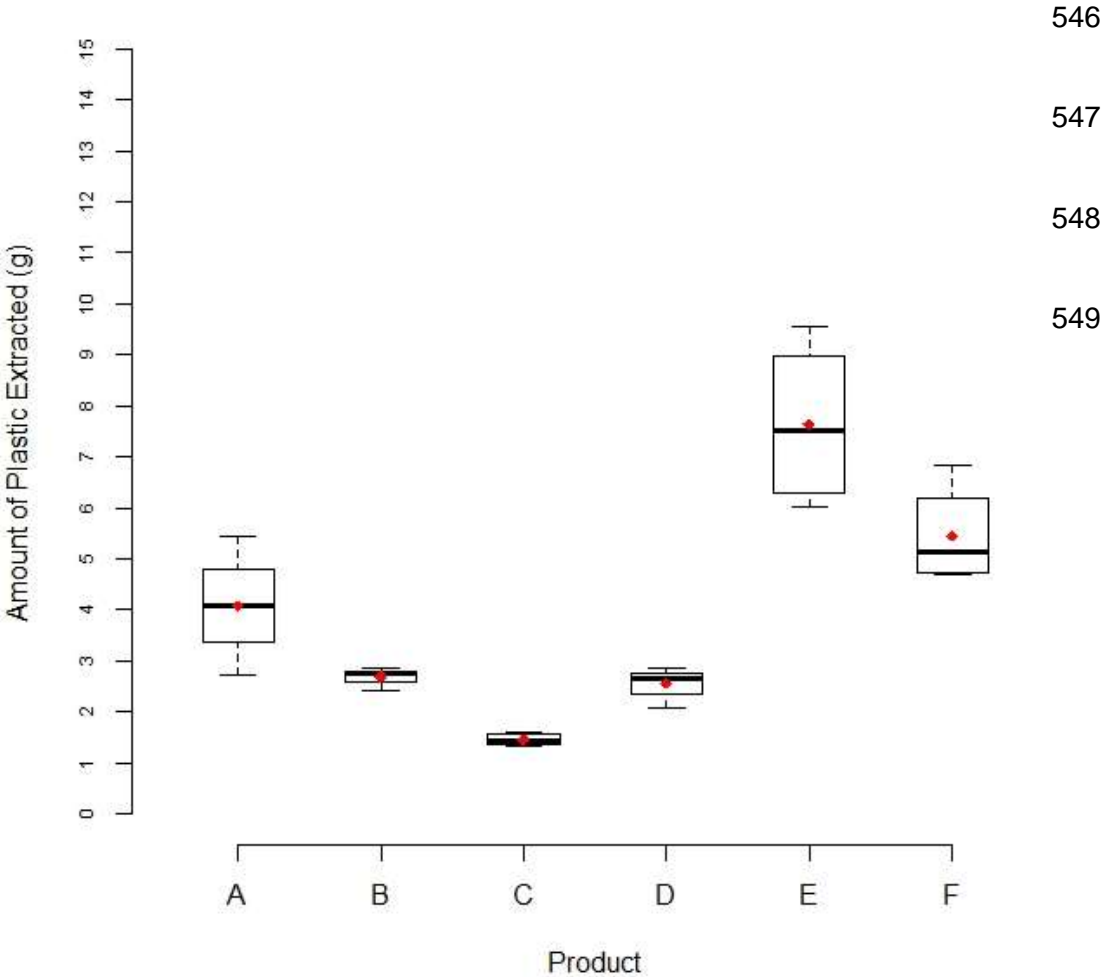


546

547

548

549

550 **Fig 1.** *Total mass of plastic microbeads extracted from six facial scrubs (A-F) per*
551 *100 mL. Diamond symbol indicates \bar{x} (n=4). The tails show both the*
552 *maximum and minimum mass obtained, and the box represents the upper*
553 *and lower quartiles. There were significant differences between the amount*
554 *of microplastic in each of the products ($p < 0.05$).*

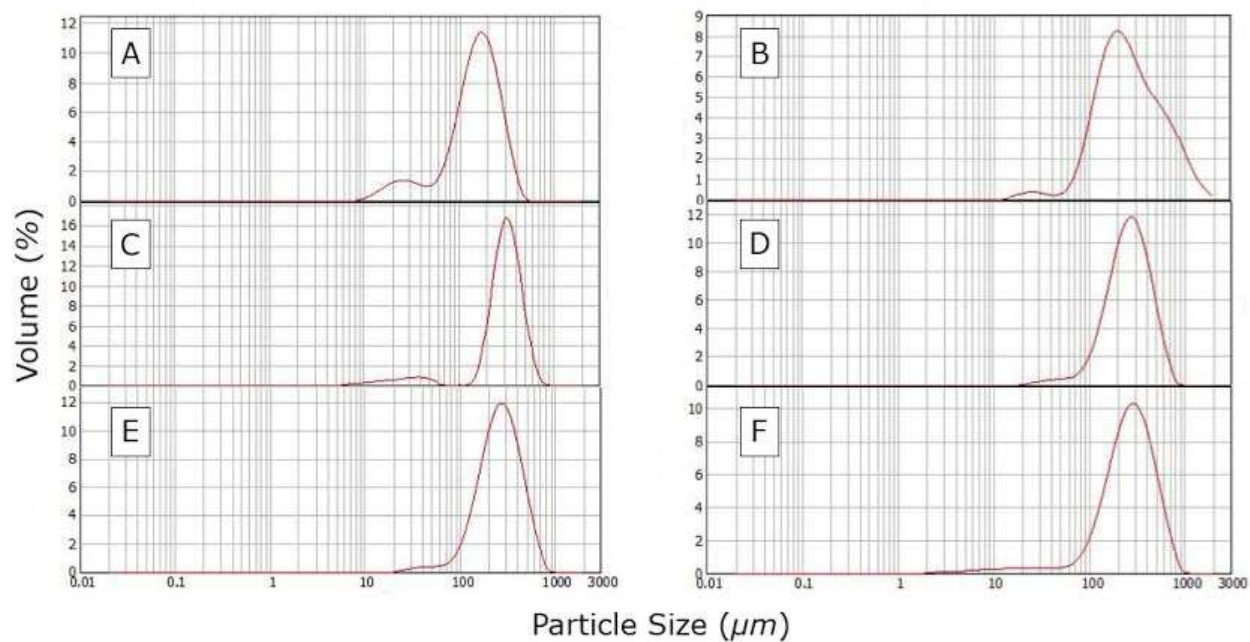

555

556 **Fig 2.** Particle size distribution of PE microbead particles extracted from six facial
557 scrubs (A-F). Determined using a Malvern Mastersizer 2000, laser particle
558 sizer.

559

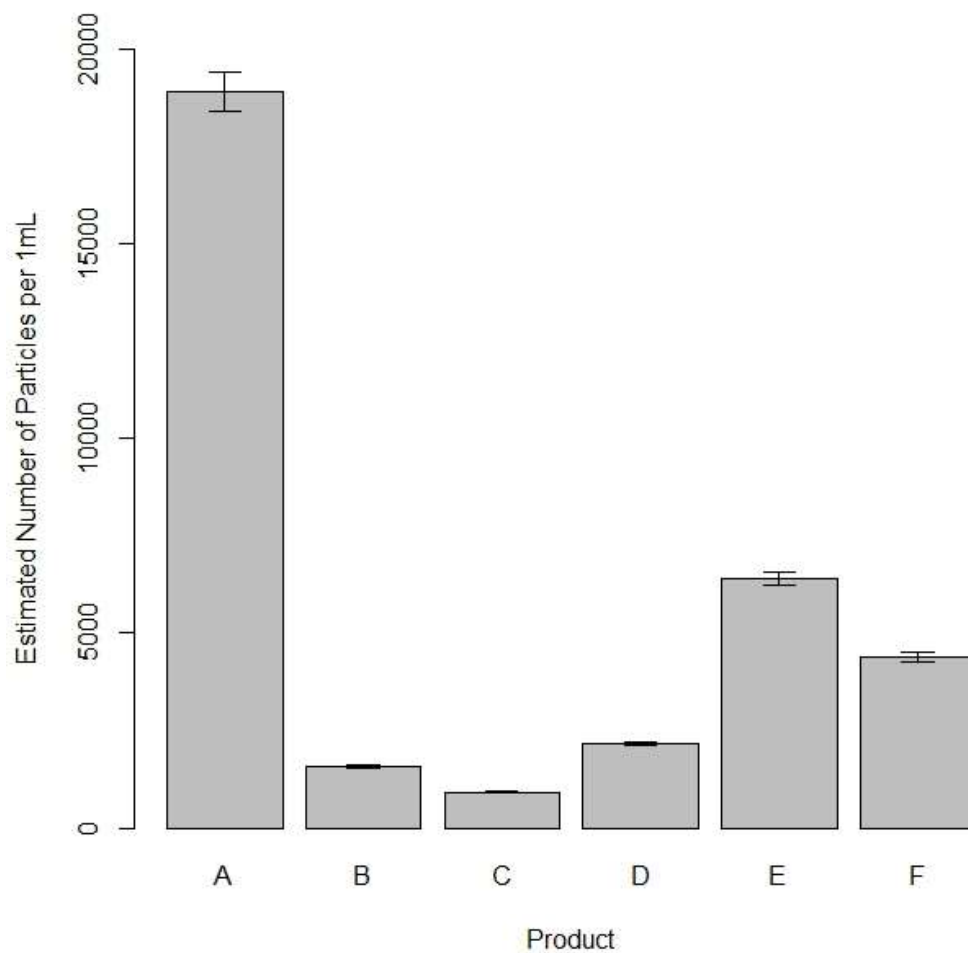


Fig 3. Estimates for the number of PE microbead particles in six brands of facial scrubs per 1mL. Calculated using data from the volume weighted mean ($n = 3$, \pm SD; correlating to the spread of the different amounts of particles calculated for high, medium and low density PE).

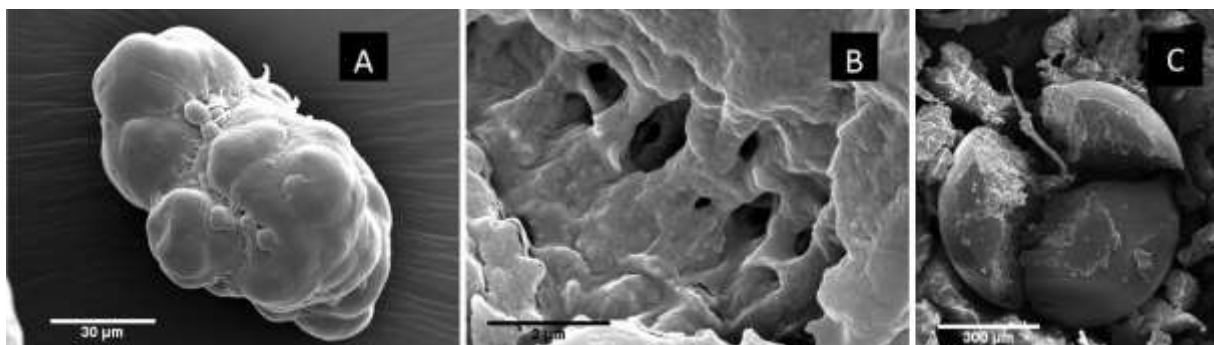


Fig 4. A-Scanning electron microscopy (SEM) of a typical rough facial scrub plastic microbead particle (9000X magnification). B- SEM of surface microbead topography (16000X magnification). C- SEM of a broken smooth spherical plastic microbead from 'product F' (900X magnification).

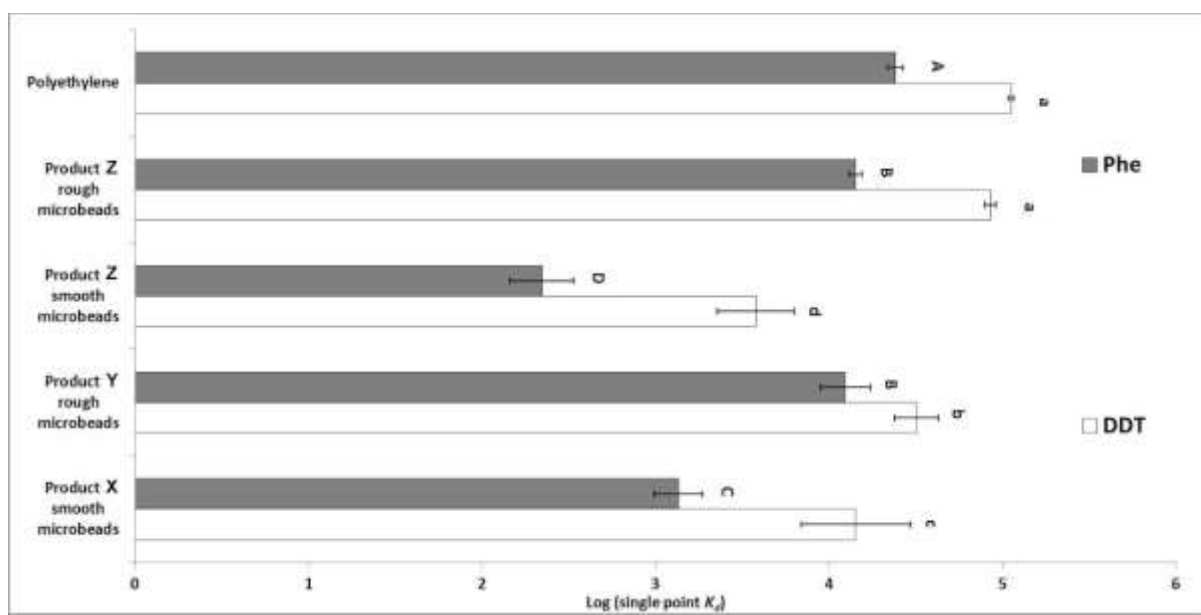


Fig 5. Single point distribution coefficients (K_d) for the sorption of a mixture of phenanthrene (Phe) and DDT onto PE particles and rough and smooth PE-microbeads extracted from cosmetic products ($n=3$, \pm SD). For each contaminant, treatments with the same letters (A-C for Phe and a-d for DDT) were not significantly different ($p < 0.05$).

580

Acknowledgements

581 The authors would like to thank Andrew Tonkin and Richard Hartley for their help
582 and expertise.

583

584 Claessens, M., et al., Occurrence and distribution of microplastics in marine sediments along the Belgian coast.
585 Marine Pollution Bulletin, 2011. 62(10): p. 2199-2204. Zitko, V. and M. Hanlon, Another Source of Pollution By
586 Plastics - Skin Cleaners With Plastic Scrubbers. Marine Pollution Bulletin, 1991. 22(1): p. 41-42. UNEP (2015)
587 Plastic in Cosmetics, ISBN: 978-92-807-3466-9 pp33 Underwood, A., Chapman, M., Richards, S., 2002. GMAV-5
588 for Windows. An analysis of variance programme. Centre for Research on Ecological Impacts of Coastal Cities.
589 Marine Ecology Laboratories, University of Sydney. Australia.

590

References

591 Andrady, A.L., 2011. Microplastics in the marine environment. Mar. Pollut. Bull.
592 doi:10.1016/j.marpolbul.2011.05.030

593 Avery-Gomm, S., O'Hara, P.D., Kleine, L., Bowes, V., Wilson, L.K., Barry, K.L., 2012.
594 Northern fulmars as biological monitors of trends of plastic pollution in the
595 eastern North Pacific. Mar. Pollut. Bull. 64, 1776–1781.
596 doi:10.1016/j.marpolbul.2012.04.017

597 Avio, C.G., Gorbi, S., Milan, M., Benedetti, M., Fattorini, D., D'Errico, G., Pauletto, M.,
598 Bargelloni, L., Regoli, F., 2015. Pollutants bioavailability and toxicological risk
599 from microplastics to marine mussels. Environ. Pollut. 198, 211–222.
600 doi:10.1016/j.envpol.2014.12.021

601 Bakir, A., Rowland, S.J., Thompson, R.C., 2014a. Transport of persistent organic
602 pollutants by microplastics in estuarine conditions. Estuar. Coast. Shelf Sci. 140,
603 14–21. doi:10.1016/j.ecss.2014.01.004

604 Bakir, A., Rowland, S.J., Thompson, R.C., 2014b. Enhanced desorption of persistent
605 organic pollutants from microplastics under simulated physiological conditions.
606 Environ. Pollut. 185, 16–23. doi:10.1016/j.envpol.2013.10.007

607 Bakir, A., Rowland, S.J., Thompson, R.C., 2012. Competitive sorption of persistent
608 organic pollutants onto microplastics in the marine environment. Mar. Pollut. Bull.
609 64, 2782–2789. doi:10.1016/j.marpolbul.2012.09.010

610 Barnes, D.K.A., Galgani, F., Thompson, R.C., Barlaz, M., 2009. Accumulation and
611 fragmentation of plastic debris in global environments. Philos. Trans. R. Soc.
612 Lond. B. Biol. Sci. 364, 1985–1998. doi:10.1098/rstb.2008.0205

613 Beat the Microbead, 2015. Products that Contain Microplastic (UK) [WWW
614 Document]. URL <http://www.beatthemicrobead.org/images/pdf/redUK.pdf>
615 (accessed 3.4.15).

616 Besseling, E., Wegner, A., Foekema, E.M., Van Den Heuvel-Greve, M.J., Koelmans,
617 A.A., 2013. Effects of microplastic on fitness and PCB bioaccumulation by the

618 lugworm *Arenicola marina* (L.). Environ. Sci. Technol. 47, 593–600.
619 doi:10.1021/es302763x

620 Boerger, C.M., Lattin, G.L., Moore, S.L., Moore, C.J., 2010. Plastic ingestion by
621 planktivorous fishes in the North Pacific Central Gyre. Mar. Pollut. Bull. 60,
622 2275–2278. doi:10.1016/j.marpolbul.2010.08.007

623 Browne, M.A., Crump, P., Niven, S.J., Teuten, E., Tonkin, A., Galloway, T.,
624 Thompson, R., 2011. Accumulation of microplastic on shorelines worldwide:
625 Sources and sinks. Environ. Sci. Technol. 45, 9175–9179.
626 doi:10.1021/es201811s

627 Browne, M.A., Dissanayake, A., Galloway, T.S., Lowe, D., Thompson, R., 2008.
628 Ingested microscopic plastic translocates to the circulatory system of the mussel,
629 *Mytilus edulis* (L). Environ. Sci. Technol. 42, 5026–5031.

630 Browne, M.A., Niven, S.J., Galloway, T.S., Rowland, S.J., Thompson, R.C., 2013.
631 Microplastic moves pollutants and additives to worms, reducing functions linked
632 to health and biodiversity. Curr. Biol. 23, 2388–2392.
633 doi:10.1016/j.cub.2013.10.012

634 Carr, A., 1987. Impact of nondegradable marine debris on the ecology and survival
635 outlook of sea turtles. Mar. Pollut. Bull. 18, 352–356. doi:10.1016/S0025-
636 326X(87)80025-5

637 Claessens, M., De Meester, S., Van Landuyt, L., De Clerck, K., Janssen, C. R. 2011
638 Occurrence and distribution of microplastics in marine sediments along the
639 Belgian coast. Mar. Pollut. Bull 62, 2199-2204.

640 Cole, M., Lindeque, P., Halsband, C., Galloway, T.S., 2011. Microplastics as
641 contaminants in the marine environment: A review. Mar. Pollut. Bull. 62, 2588–
642 2597. doi:10.1016/j.marpolbul.2011.09.025

643 DEFRA, 2002. Sewage Treatment in the UK; UK Implementation of the EC Urban
644 Waste Water Treatment Directive. London.

645 Denuncio, P., Bastida, R., Dassis, M., Giardino, G., Gerpe, M., Rodríguez, D., 2011.
646 Plastic ingestion in Franciscana dolphins, *Pontoporia blainvillei* (Gervais and
647 d’Orbigny, 1844), from Argentina. Mar. Pollut. Bull. 62, 1836–1841.
648 doi:10.1016/j.marpolbul.2011.05.003

649 Desforges, J.P.W., Galbraith, M., Dangerfield, N., Ross, P.S., 2014. Widespread
650 distribution of microplastics in subsurface seawater in the NE Pacific Ocean.
651 Mar. Pollut. Bull. 79, 94–99. doi:10.1016/j.marpolbul.2013.12.035

652 Driedger, A.G.J., Dürr, H.H., Mitchell, K., Van Cappellen, P., 2015. Plastic debris in
653 the Laurentian Great Lakes: A review. J. Great Lakes Res. 41, 9–19.
654 doi:10.1016/j.jglr.2014.12.020

655 Eerkes-Medrano, D., Thompson, R.C., Aldridge, D.C., 2015. Microplastics in
656 freshwater systems: a review of the emerging threats, identification of
657 knowledge gaps and prioritisation of research needs. *Water Res.* 75, 63–82.
658 doi:10.1016/j.watres.2015.02.012

659 Eriksen, M., Mason, S., Wilson, S., Box, C., Zellers, A., Edwards, W., Farley, H.,
660 Amato, S., 2013. Microplastic pollution in the surface waters of the Laurentian
661 Great Lakes. *Mar. Pollut. Bull.* 77, 177–182.
662 doi:10.1016/j.marpolbul.2013.10.007

663 Fendall, L.S., Sewell, M.A., 2009. Contributing to marine pollution by washing your
664 face: Microplastics in facial cleansers. *Mar. Pollut. Bull.* 58, 1225–1228.
665 doi:10.1016/j.marpolbul.2009.04.025

666 Fowler, C.W., 1987. Marine debris and northern fur seals: A case study. *Mar. Pollut.*
667 *Bull.* 18, 326–335. doi:10.1016/S0025-326X(87)80020-6

668 Gall, S.C., Thompson, R.C., 2015. The impact of debris on marine life. *Mar. Pollut.*
669 *Bull.* 92, 170–179. doi:10.1016/j.marpolbul.2014.12.041

670 Gallagher, A., Rees, A., Rowe, R., Stevens, J., Wright, P., 2015. Microplastics in the
671 Solent estuarine complex, UK: An initial assessment [WWW Document]. *Mar.*
672 *Pollut. Bull.* doi:10.1016/j.marpolbul.2015.04.002

673 Goldstein, M.C., Rosenberg, M., Cheng, L., 2012. Increased oceanic microplastic
674 debris enhances oviposition in an endemic pelagic insect. *Biol. Lett.*
675 doi:10.1098/rsbl.2012.0298

676 Gouin, T., Avalos, J., Brunning, I., Brzuska, K., Graaf, de J., Kaumanns, J., Konong,
677 T., Meyberg, M., Rettinger, K., Schlatter, H., Thomas, J., Welie, van R., Wolf, T.,
678 2015. Use of Micro-Plastic Beads in Cosmetic Products in Europe and Their
679 Estimated Emissions to the North Sea Environment. *SOFW J.* 1–33.

680 Gouin, T., Roche, N., Lohmann, R., Hodges, G., 2011. A thermodynamic approach
681 for assessing the environmental exposure of chemicals absorbed to microplastic.
682 *Environ. Sci. Technol.* 45, 1466–72. doi:10.1021/es1032025

683 Graham, E.R., Thompson, J.T., 2009. Deposit- and suspension-feeding sea
684 cucumbers (Echinodermata) ingest plastic fragments. *J. Exp. Mar. Bio. Ecol.*
685 368, 22–29. doi:10.1016/j.jembe.2008.09.007

686 Gregory, M.R., 1996. Plastic scrubbers' in hand cleansers: A further (and minor)
687 source for marine pollution identified. *Mar. Pollut. Bull.* 32, 867–871.
688 doi:10.1016/S0025-326X(96)00047-1

689 Harrison, J.P., Schratzberger, M., Sapp, M., Osborn, A.M., 2014. Rapid bacterial
690 colonization of low-density polyethylene microplastics in coastal sediment
691 microcosms. *BMC Microbiol.* 14, 232. doi:10.1186/s12866-014-0232-4

692 Hopewell, J., Dvorak, R., Kosior, E., 2009. Plastics recycling: challenges and
693 opportunities. *Philos. Trans. R. Soc. Lond. B. Biol. Sci.* 364, 2115–2126.
694 doi:10.1098/rstb.2008.0311

695 Koelmans, A.A., Besseling, E., Wegner, A., Foekema, E.M., 2013. Plastic as a
696 carrier of POPs to aquatic organisms: A model analysis. *Environ. Sci. Technol.*
697 47, 7812–7820. doi:10.1021/es401169n

698 Laist, D., 1997. Impacts of Marine Debris: Entanglement of Marine Life in Marine
699 Debris Including a Comprehensive List of Species with Entanglement and
700 Ingestion Records, in: *Marine Debris*. Springer, New York, pp. 99–135.

701 Law, K.L., Morét-Ferguson, S., Maximenko, N.A., Proskurowski, G., Peacock, E.E.,
702 Hafner, J., Reddy, C.M., 2010. Plastic accumulation in the North Atlantic
703 subtropical gyre. *Science* 329, 1185–1188. doi:10.1126/science.1192321

704 Law, K.L., Thompson, R.C., 2014. Microplastics in the seas. *Science* (80-.). 345,
705 144–145. doi:10.1126/science.1254065

706 Leslie, H.A., Velzen, M.J.M. van, Vethaak, A.D., 2013. Microplastic survey of the
707 Dutch environment; Novel data set of microplastics in North Sea sediments,
708 treated wastewater effluents and marine biota [WWW Document]. URL
709 http://www.ivm.vu.nl/en/Images/IVM_report_Microplastic_in_sediment_STP_Biota_2013_tcm53-409860.pdf
710

711 Lusher, A.L., Burke, A., O'Connor, I., Officer, R., 2014. Microplastic pollution in the
712 Northeast Atlantic Ocean: Validated and opportunistic sampling. *Mar. Pollut. Bull.*
713 88, 325–333. doi:10.1016/j.marpolbul.2014.08.023

714 Marine Conservation Society, 2012. Micro plastics in personal care products [WWW
715 Document]. URL <http://www.mcsuk.org/downloads/pollution/positionpaper-microplastics-august2012.pdf> (accessed 5.14.15).
716

717 Murray, F., Cowie, P.R., 2011. Plastic contamination in the decapod crustacean
718 *Nephrops norvegicus* (Linnaeus, 1758). *Mar. Pollut. Bull.* 62, 1207–1217.
719 doi:10.1016/j.marpolbul.2011.03.032

720 Plastics Europe, 2014. The facts 2014. An analysis of European plastics production,
721 demand and waste data [WWW Document]. URL www.plasticseurope.org
722 (accessed 4.15.15).

723 Rochman, C.M., Hoh, E., Kurobe, T., Teh, S.J., 2013. Ingested plastic transfers
724 hazardous chemicals to fish and induces hepatic stress. *Sci. Rep.* 3, 3263.
725 doi:10.1038/srep03263

726 Statista, 2013. Number of women using facial scrubs and masks in the United
727 Kingdom (UK) in 2013, by frequency of use (in 1,000) [WWW Document]. URL
728 <http://www.statista.com/statistics/302541/scrubs-and-masks-usage-frequency-in-the-uk/>
729 (accessed 3.23.15).

730 Teuten, E.L., Rowland, S.J., Galloway, T.S., Thompson, R.C., 2007. Potential for
731 plastics to transport hydrophobic contaminants. *Environ. Sci. Technol.* 41,
732 7759–7764. doi:10.1021/es071737s

733 The World Bank, 2013. Population of the United Kingdom [WWW Document]. URL
734 <http://data.worldbank.org/country/united-kingdom> (accessed 5.14.15).

735 Thompson, R.C., Moore, C.J., vom Saal, F.S., Swan, S.H., 2009a. Plastics, the
736 environment and human health: current consensus and future trends. *Philos.*
737 *Trans. R. Soc. Lond. B. Biol. Sci.* 364, 2153–2166. doi:10.1098/rstb.2009.0053

738 Thompson, R.C., Swan, S.H., Moore, C.J., vom Saal, F.S., 2009b. Our plastic age.
739 *Philos. Trans. R. Soc. Lond. B. Biol. Sci.* 364, 1973–1976.
740 doi:10.1098/rstb.2009.0054

741 Underwood, A., Chapman, M., Richards, S., 2002. GMAV-5 for Windows. An
742 analysis of variance programme. Centre for Research on Ecological Impacts of
743 Coastal Cities. Marine Ecology Laboratories, University of Sydney. Australia.

744 UNEP (2015) Plastic in Cosmetics, ISBN: 978-92-807-3466-9 pp33

745 Van Cauwenberghe, L., Vanreusel, A., Mees, J., Janssen, C.R., 2013. Microplastic
746 pollution in deep-sea sediments. *Environ. Pollut.*
747 doi:10.1016/j.envpol.2013.08.013

748 Van Franeker, J.A., Blaize, C., Danielsen, J., Fairclough, K., Gollan, J., Guse, N.,
749 Hansen, P.L., Heubeck, M., Jensen, J.K., Le Guillou, G., Olsen, B., Olsen, K.O.,
750 Pedersen, J., Stienen, E.W.M., Turner, D.M., 2011. Monitoring plastic ingestion
751 by the northern fulmar *Fulmarus glacialis* in the North Sea. *Environ. Pollut.* 159,
752 2609–2615. doi:10.1016/j.envpol.2011.06.008

753 Water Environment Federation, 2003. Wastewater Treatment Plant Design, 1st ed.
754 IWA Publishing, Virginia, USA.

755 Woolfe, K.J., Michibayashi, K., 1995. “BASIC” entropy grouping of laser-derived
756 grain-size data: An example from the Great Barrier Reef. *Comput. Geosci.*
757 doi:10.1016/0098-3004(94)00092-9

758 Wright, S.L., Rowe, D., Thompson, R.C., Galloway, T.S., 2013a. Microplastic
759 ingestion decreases energy reserves in marine worms. *Curr. Biol.* 23, R1031–
760 R1033. doi:10.1016/j.cub.2013.10.068

761 Wright, S.L., Thompson, R.C., Galloway, T.S., 2013b. The physical impacts of
762 microplastics on marine organisms: A review. *Environ. Pollut.* 178, 483–492.
763 doi:10.1016/j.envpol.2013.02.031

764 Zettler, E.R., Mincer, T.J., Amaral-Zettler, L.A., 2013. Life in the “plastisphere”:
765 Microbial communities on plastic marine debris. *Environ. Sci. Technol.* 47,
766 7137–7146. doi:10.1021/es401288x

767 Zitko, V., Hanlon, M. 1991 Another Source of Pollution By Plastics - Skin Cleaners
768 With Plastic Scrubbers. Mar. Pollut. Bull **22**, 41-42.

769

770